



Gesteinkörnung : 4/16R
Petrographischer Typ : Alpine Moräne - Oberheinkies und sand

Normative Teil

Werte auf die sich der producent verpflichtet

Lieferkörnung

Norme

Kategorie

4 16

Norme XP P 18-545 Article 10 - EN 12620 et EN 13139


Code A

	0.063	d/2 2	d 4	5	5.6	6.3	D/2 8	10	12.5	D 16	20	1.4D 22.4	2D 31.5	f	FI	W
Ausmas							35									
V.S.S.+U	2.1	6	20				66			100					24.00	
V.S.S.	1.5	5	15				60			99				1.50	20.00	
V.S.I.			0				25			90		98	100			
V.S.I.-U			0				19			85		97				

Informative Teil Production resultat

von 02/05/23 bis 28/08/23

	0.063	2	4	5	5.6	6.3	8	10	12.5	16	20	22.4	31.5	f	FI	W
Maxi	0.1	0	10	22	29	42	59	75	90	99	100	100	100	0.09	15.61	4.6
Xk+1.25xAbstand-type	0.0	0	7	17	24	35	54	75	91	99	100	100	100	0.05		4.0
Mittelwert Xf	0.0	0	4	12	17	25	44	63	82	98	100	100	100	0.02	14.60	2.6
Xk-1.25xAbstand-type	0.0	0	1	6	10	16	33	50	73	96	100	100	100	0.00		1.3
Mini	0.0	0	2	7	11	17	33	46	69	95	100	100	100	0.00	12.02	0.5
Abstand-type	0.02	0.1	2.3	4.4	5.6	7.4	8.7	9.7	6.9	1.2	0.0	0.0	0.0	0.023	1.497	1.10

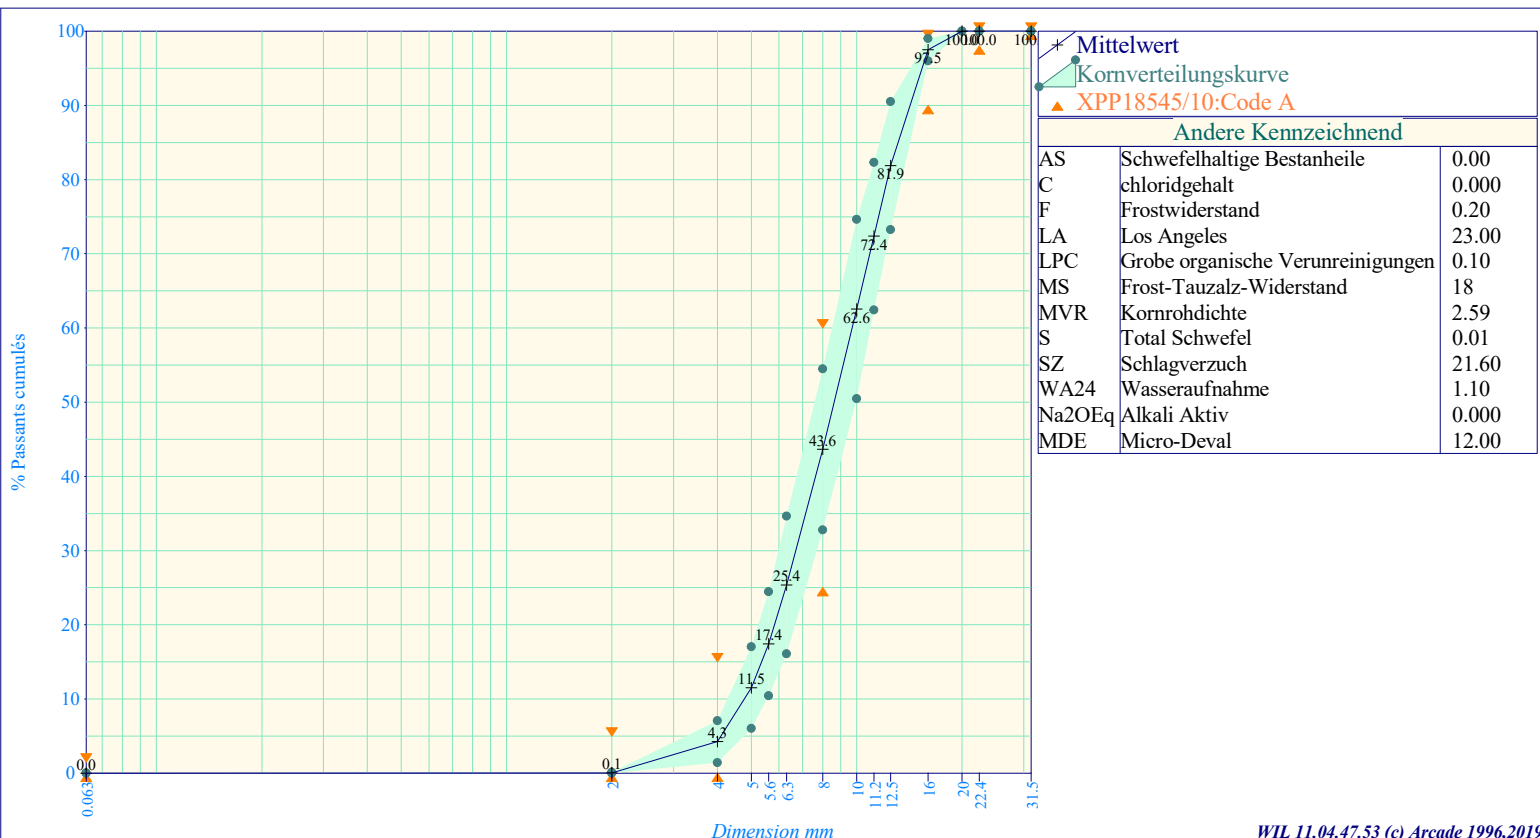

Dimension mm

WIL 11.04.47.53 (c) Arcade 1996,2019