



Gesteinkörnung : 2/8 rundkies
Petrographischer Typ : Alpine Moräne - Oberrheinkies und sand

Normative Teil

Werte auf die sich der producent verpflichtet

Lieferkörnung

Norme

Kategorie

2

8

Norme XP P 18-545 Article 10 - EN 12620 et EN 13139


EN 12620

		d/2	d	D/2			D		1.4D	2D			
	0.063	1	2	4	5	6.3	8	10	11.2	16	f	FI	W
Ausmas			20	20			15						
V.S.S.+U		6	25	25			100		100			24.00	
V.S.S.		5	20	20			99		100		1.50	20.00	
V.S.I.			0	0			85		98	100			
V.S.I.-U			0	0			80		97				

Informative Teil Production resultat

von 16/09/24 bis 28/07/25

	0.063	1	2	4	5	6.3	8	10	11.2	16	f	FI	W
Maxi	0.2	1	1	20	53	83	99	100	100	100	0.16	14.71	6.2
Xk+1.25xAbstand-type	0.1	0	0	21	50	82	100	100	100	100	0.07		
Mittelwert Xf	0.0	0	0	14	36	68	96	100	100	100	0.02	9.03	4.3
Xk-1.25xAbstand-type	0.0	0	0	7	22	53	91	100	100	100	0.00		
Mini	0.0	0	0	4	13	43	85	100	100	100	0.00	0.00	1.1
Abstand-type	0.04	0.2	0.2	5.3	11.3	11.4	3.8	0.0	0.0	0.0	0.040	3.583	1.50

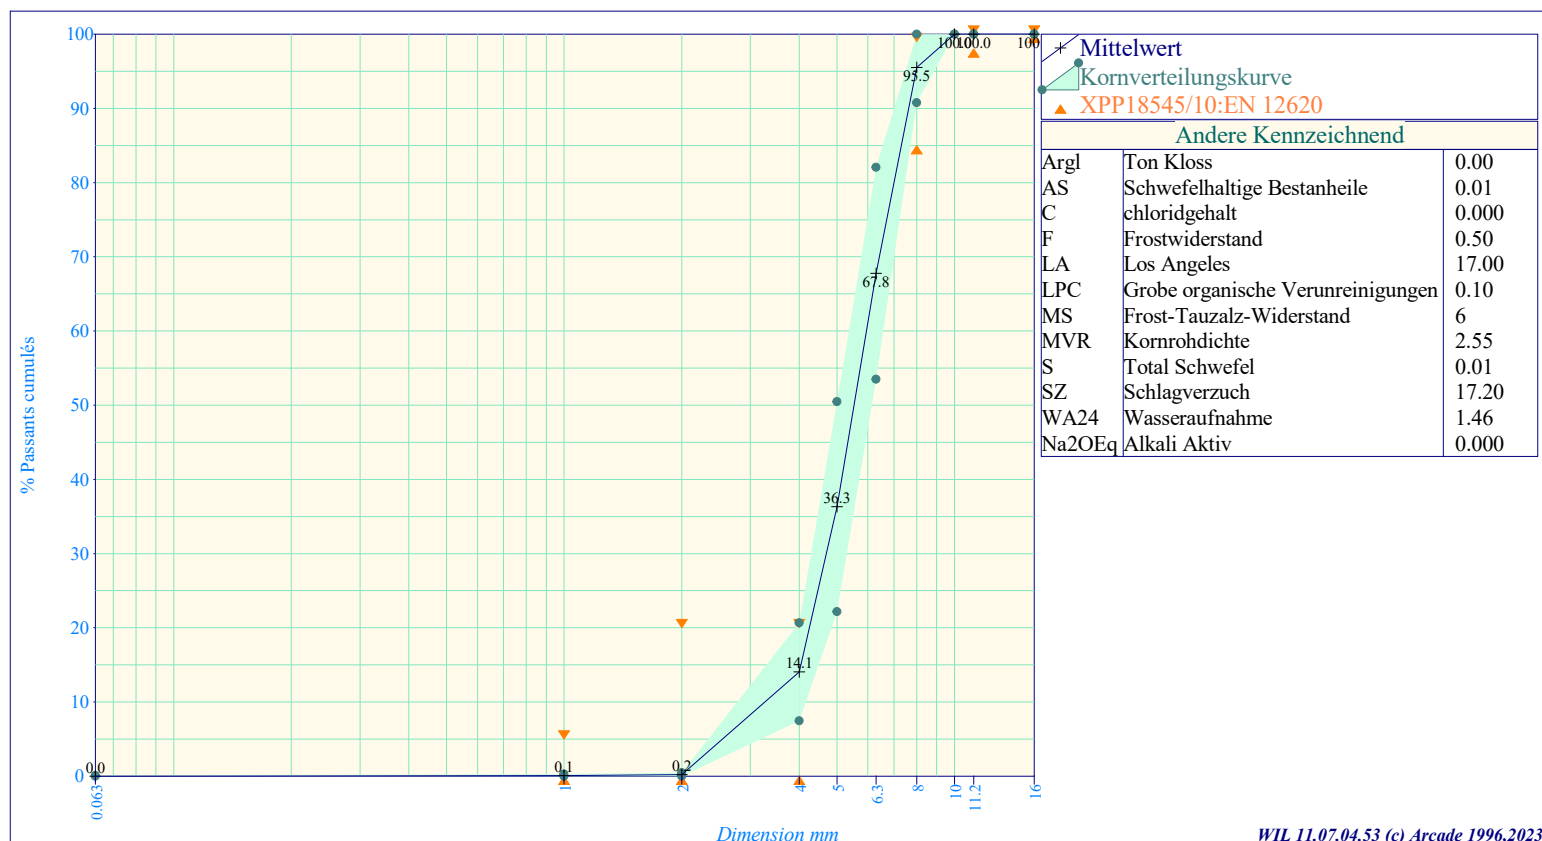

Dimension mm

WIL 11.07.04.53 (c) Arcade 1996,2023